

# Mechanical Theory and Systems

<https://mts.cultechpub.com/mts>

Cultech Publishing

## Article

# Comparative Evaluation of Cryogenic and Flood Cooling for Precision and Sustainable Machining of Inconel 718

**Prashant S. Jadhav\*, Rohit Magdum, Shailesh Shirguppikar, Ramadevi V. Salunkhe**

K. E. Society's, Rajarambapu Institute of Technology, Rajaramnagar, Shivaji University, Kolhapur, Maharashtra, India

\*Corresponding author: Prashant S. Jadhav, [prashant.jadhav@ritindia.edu](mailto:prashant.jadhav@ritindia.edu)

## Abstract

This study evaluates the machinability of Inconel 718—a nickel-based superalloy widely used in aerospace, defence, and high-performance applications under conventional flood cooling and cryogenic cooling with liquid nitrogen (LN<sub>2</sub>). Its low thermal conductivity, strain-hardening tendency, and abrasive microstructure make precision machining challenging. The effects of spindle speed, feed rate, and depth of cut were investigated using Taguchi's L27 design on surface roughness (Ra), tool wear (TW), cutting forces (CF), power consumption (P), and machining noise (N). Cryogenic cooling outperformed flood cooling, reducing surface roughness and tool wear by up to 30%, lowering cutting forces and noise, and minimizing vibration and deflection. Chip morphology and economic analysis further confirmed its industrial feasibility, showing a 38% cost benefit due to reduced tool consumption and elimination of coolant disposal. Overall, cryogenic cooling enhances precision, dimensional control, energy efficiency, and sustainability, demonstrating strong potential for industrial adoption in applications demanding high accuracy and material performance.

## Keywords

Inconel 718, Precision machining, Sustainability, Cryogenic cooling, Liquid nitrogen(LN<sub>2</sub>), Power consumption, Surface roughness, Cost assessment

## Article History

Received: 25 August 2025

Revised: 10 September 2025

Accepted: 17 September 2025

Available: 26 September 2025

## Copyright

© 2025 by the authors. This article is published by the Cultech Publishing Sdn. Bhd. under the terms of the Creative Commons Attribution 4.0 International License (CC BY 4.0): <https://creativecommons.org/licenses/by/4.0/>

## 1. Introduction

Nickel-based superalloys are extensively employed in critical sectors due to their exceptional mechanical and thermal properties, which include high yield strength, creep resistance, fatigue resistance, and corrosion resistance at elevated temperatures [1–3]. These alloys find widespread applications in aerospace engines, gas turbines, nuclear power plants, naval systems, and automotive components where reliability under extreme environments is mandatory [4–6]. Among them, Inconel 718 has become one of the most widely used alloys owing to its superior hot hardness, thermal stability, and excellent performance in aggressive operating environments [7–9].


Despite these advantages, Inconel 718 is classified as a “difficult-to-machine material” because of its low thermal conductivity, rapid work hardening, and abrasive carbide particles that accelerate tool wear [10–12]. These characteristics lead to high cutting forces, elevated tool–workpiece interface temperatures, and poor machinability, particularly when tight dimensional tolerances and superior surface integrity are required [13–15]. Researchers have long emphasized that ensuring geometrical accuracy, tool life, and productivity while machining Inconel 718 remains a major industrial challenge [16–18].

To address these issues, several cooling and lubrication techniques have been investigated. Conventional flood cooling, the most common method, reduces cutting temperature and friction at the tool–workpiece interface [19]. However, flood cooling has significant drawbacks, including excessive use of cutting fluids, disposal costs, operator health hazards, and environmental pollution [20–22]. Moreover, mineral oil-based coolants often fail to provide adequate cooling under high-speed machining conditions, leading to thermal distortion, tool vibration, and inconsistent lubrication [23,24].

Sustainable machining approaches such as dry machining, minimum quantity lubrication (MQL), nanofluid-assisted MQL, and hybrid cooling have been explored to overcome these limitations [25,26]. Dry machining eliminates fluid use but results in excessive tool wear in superalloys [27]. MQL and nanofluid-assisted cooling improve tribological behavior, reduce cutting temperature, and enhance surface finish, but their limited cooling capacity restricts their effectiveness for machining Inconel 718 at aggressive cutting conditions [28,29]. Hybrid cooling systems, which combine MQL with cryogenic jets, have shown promise but increase process complexity [30].

Cryogenic cooling, particularly using liquid nitrogen ( $\text{LN}_2$ ), has gained significant attention as an environmentally friendly and highly efficient alternative. It provides rapid heat dissipation, reduces thermal loads, and eliminates coolant disposal requirements, making it both technically and ecologically advantageous [31,32]. Studies have demonstrated that cryogenic cooling substantially lowers cutting temperature, tool wear, and residual stresses while improving surface roughness and dimensional stability [33–35]. Some studies further showed cryogenic machining enhances tool life and chip control, thereby improving process stability [36,37].

From a sustainability perspective, few studies have emphasized that cryogenic cooling not only improves machinability but also reduces energy consumption and environmental impact [38–40]. Recent review confirm that cryogenic cooling offers a transformative pathway toward precision and sustainable machining of nickel-based superalloys [41].

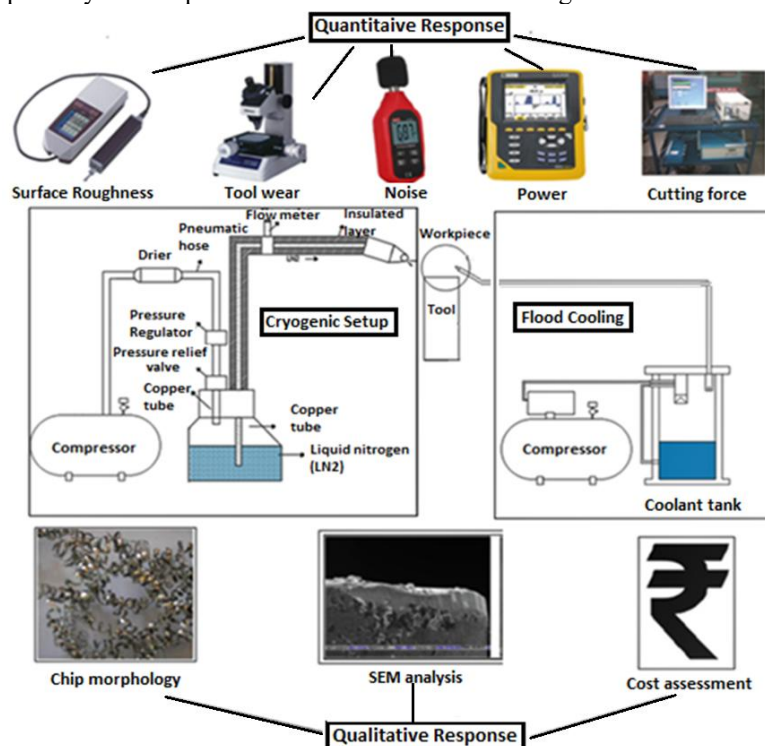

**Figure 1.** Schematics of the study.


Despite these advances, comprehensive studies that simultaneously consider precision machining indicators (surface roughness, tool wear, forces, and machining noise) and economic feasibility (cost, tool consumption, and coolant disposal) remain limited. This motivates the present work, which compares cryogenic cooling and flood cooling in the turning of Inconel 718, with a detailed evaluation of machining performance, cost assessment, and chip morphology to establish the industrial viability of cryogenic machining. The proposed work's schematics are shown in Figure 1.

## 2. Experimental Methodology

Based on a thorough assessment of the literature, three levels were chosen as the input parameters for this work: spindle speed ( $V_c$ ), cutting feed ( $f$ ), and depth of cut ( $a_p$ ). According to reports, Taguchi's experimental design offers strong, high-quality, and economical design solutions. The method can extract detailed data from the fewest experimental runs and organizing the results in a methodical manner [42]. Thus, the impact of three key process variables is observed on performance metrics like surface roughness (SR), power consumption (P), machining noise (N), tool wear (TW), and cutting forces (CF) is assessed in this work using Taguchi's L27 orthogonal array. The details of experimental setup are shown in Table 1 and Figure 2 whereas, the mechanical properties and composition of Inconel 718 are shown in Table 2.

**Table 1.** Experimental details of the study

| Particular                           | Specification   |
|--------------------------------------|---|
| Work piece                           | Inconel 718 alloy ( $\Phi$ 40 mm X 200 mm)  |
| Machine                              | MTAB Max Turn   |
| Cutting Insert                       | TiN-MT-TiCN- $Al_2O_3$ ; Kennametal make, Grade- CNMG 120408-KC5010   |
| Tool Holder                          | MTJNR 2525 M16  |
| Cutting tool geometry                | Cutting edge angle: $80^\circ$ ; rake angle: $-8^\circ$ , clearance angle: $-8^\circ$ ,<br>Nose radius: 1 mm.   |
| DOE                                  | L-27 (Taguchi's array)  |
| Input Parameters (3 levels)          | Cutting speed: $V_c$ (50 m/min, 80 m/min, 110 m/min),<br>Cutting feed: $f$ (0.08 mm/rev, 0.1 mm/rev, 0.12 mm/rev),<br>Depth of cut: $a_p$ (0.4 mm, 0.6 mm, 0.8 mm)  |
| Performance Attributes               | Surface roughness, power consumption, machining noise, tool wear and cutting forces   |
| Machining strategy and coolants used | Cryogenic: Liquid nitrogen ( $LN_2$ ) as coolant, compressed air: 5 bar,<br>Flow rate: 0.50 L/min, brass nozzle ( $\Phi$ 1.2 mm) positioned at 30 mm distance from the cutting tool.<br>Flood: A neat cutting oil-137 as coolant, oil pressure: 4 bar,<br>Flow rate: 30 L/min, nozzles ( $\Phi$ 2.5 mm) positioned within 20 mm distance from the machining zone. |

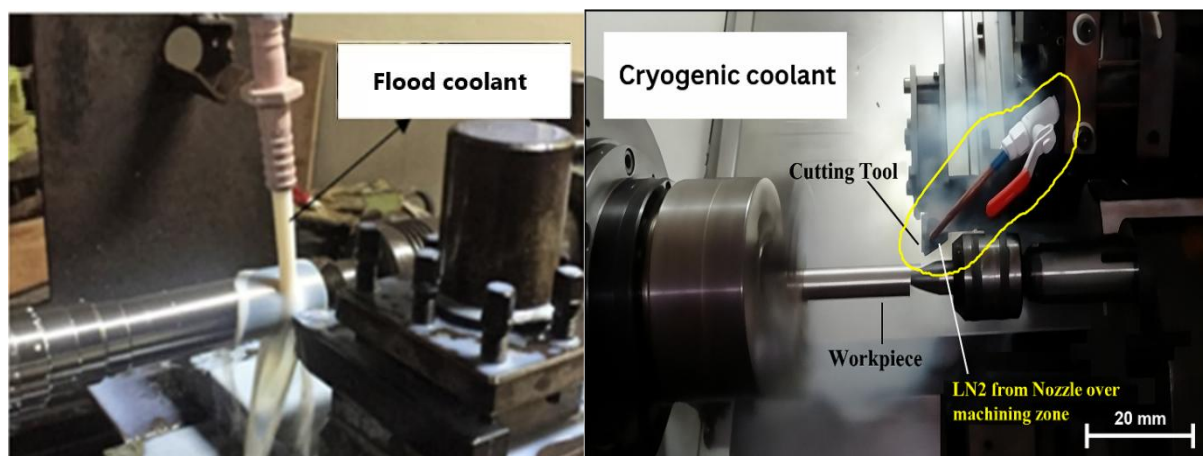

**Figure 2.** Experimental setup. (a) flood coolant, (b) cryogenic coolant.

**Table 2.** Mechanical properties of Inconel 718 [43].

| Composition (%) | C- 0.10, Al- 0.40, Co- 1 max, Cr- 21.5, Fe- 5 max, Mo-9, Ti- 0.40, N- 0.015, S- 0.015 (Balanced Ni) |               |                        |                       |                             |
|-----------------|---|---------------|------------------------|-----------------------|-----------------------------|
| Properties      | Yield strength (MPa)  | Hardness (HV) | Tensile strength (MPa) | Elastic Modulus (GPa) | Thermal Conductivity (W/mK) |
| Values          | 615   | 260           | 880                    | 210                   | 9.8                         |

### 3. Measurement of Responses

To record the values of the responses such as surface roughness (SR), power consumption (P), machining noise (N), tool wear (TW), and cutting forces (CF), the tests are carried out using Taguchi's L27 orthogonal array. Every experiment is carried out twice, and for greater accuracy, the mean reading is taken for the analysis.

#### 3.1 Measurement of surface roughness (SR)

The Talysurf surface Mitutoyo's (SJ-178) roughness machine is used to measure the surface roughness (SR) as shown in Figure 3. It was measured four times and the average value, Ra in micron, was recorded as the final result. This is done to get an accurate reading and to prevent human error.



**Figure 3.** Measurement of surface roughness.

#### 3.2 Measurement of Power consumption (P)

The CNC machine's electric panel is connected to a Fluke 435 power analyzer (energy meter) equipment, which measures both active and reactive power. This provides each trial's power consumption (P) in watts (W) and recorded as final reading.

#### 3.3 Measurement of Noise (N)

Using a Lutron SL-401 portable noise meter, the noise concentration generated during turning is measured in decibels (dB) while all other laboratory equipment is turned off in a separate workplace. To obtain the most accurate measurement of machining noise, five readings of the noise values are obtained, and the average of the readings is recorded.

#### 3.4 Tool wear measurement (TW)

Using a Mitutoyo Toolmaker microscope, tool wear (TW) was measured and recorded in millimeters (mm) as shown in Figure 4. Under 10X magnification, the difference between the initial and final readings is recorded.



**Figure 4.** Measurement of tool wear.

The measurement is performed by aligning the cutting-edge perpendicular to the optical axis and using the microscope's digital or scale-based measurement system to determine the wear dimensions with micrometer precision. Multiple points along the edge are measured to calculate an average wear value. Images are captured for documentation and comparative analysis under different machining conditions. This method provides accurate and repeatable assessment of tool wear, enabling correlation with surface finish, cutting forces, and tool life.

### 3.5 Cutting force measurement (CF)

Using a Kistler tool dynamometer 5233A equipped with a Dyno-Ware data collection system, the cutting force (CF) was measured and expressed in newtons (N). This software plots all the force components, recording the average cutting force for each rotation.

## 4. Result and Discussion

The design of experiments, machining parameters, and results for two settings i.e. for flood machining and cryogenic machining are displayed in Table 3. It shows that, when compared to flood machining, the values of all attributes attained during cryogenic machining are significantly lower. This suggests that, while cutting the Inconel 718 workpiece, cryogenic machining has outperformed the flood machining.


**Table 3.** Comparative analysis of flood machining vs cryogenic machining.

| S.N. | Vc  | f    | ap  | Flood machining |         |        |       |        | Cryogenic machining |         |       |       |        |
|------|-----|------|-----|-----------------|---------|--------|-------|--------|---------------------|---------|-------|-------|--------|
|      |     |      |     | SR              | P       | N      | TW    | CF     | SR                  | P       | N     | TW    | CF     |
| 1    | 50  | 0.08 | 0.4 | 0.948           | 3134.09 | 90.86  | 0.063 | 267.30 | 0.771               | 2321.55 | 77.00 | 0.074 | 189.13 |
| 2    | 50  | 0.08 | 0.6 | 1.557           | 4084.34 | 99.14  | 0.094 | 292.31 | 1.266               | 3025.40 | 84.02 | 0.110 | 206.82 |
| 3    | 50  | 0.08 | 0.8 | 0.648           | 4669.19 | 96.22  | 0.094 | 292.00 | 0.527               | 3458.66 | 81.54 | 0.110 | 206.60 |
| 4    | 50  | 0.1  | 0.4 | 0.797           | 5469.00 | 100.04 | 0.110 | 324.05 | 0.659               | 4051.11 | 84.78 | 0.128 | 229.28 |
| 5    | 50  | 0.1  | 0.6 | 0.897           | 4024.35 | 95.32  | 0.096 | 315.20 | 0.730               | 2981.00 | 80.78 | 0.113 | 223.02 |
| 6    | 50  | 0.1  | 0.8 | 1.530           | 4997.61 | 93.31  | 0.089 | 243.91 | 1.244               | 3701.94 | 79.08 | 0.104 | 172.57 |
| 7    | 50  | 0.12 | 0.4 | 0.600           | 6317.93 | 100.55 | 0.095 | 290.47 | 0.488               | 4679.95 | 85.21 | 0.111 | 205.52 |
| 8    | 50  | 0.12 | 0.6 | 1.121           | 3834.14 | 89.47  | 0.086 | 336.57 | 0.912               | 2840.11 | 75.82 | 0.100 | 238.14 |
| 9    | 50  | 0.12 | 0.8 | 0.542           | 4669.19 | 98.77  | 0.103 | 385.80 | 0.441               | 3458.66 | 83.70 | 0.120 | 272.97 |
| 10   | 80  | 0.08 | 0.4 | 0.793           | 3998.85 | 93.33  | 0.077 | 278.26 | 0.645               | 2962.11 | 79.10 | 0.090 | 196.88 |
| 11   | 80  | 0.08 | 0.6 | 0.721           | 4951.46 | 102.33 | 0.104 | 313.54 | 0.586               | 3667.75 | 86.72 | 0.121 | 221.84 |
| 12   | 80  | 0.08 | 0.8 | 0.564           | 3282.52 | 92.08  | 0.070 | 253.56 | 0.458               | 2431.49 | 78.03 | 0.082 | 179.41 |
| 13   | 80  | 0.1  | 0.4 | 0.549           | 4151.70 | 95.96  | 0.086 | 264.37 | 0.446               | 3075.33 | 81.32 | 0.100 | 187.06 |
| 14   | 80  | 0.1  | 0.6 | 0.802           | 5606.24 | 94.68  | 0.068 | 293.83 | 0.652               | 4152.77 | 80.24 | 0.080 | 207.90 |
| 15   | 80  | 0.1  | 0.8 | 1.849           | 6362.80 | 97.01  | 0.092 | 339.09 | 1.503               | 4713.19 | 82.21 | 0.107 | 239.92 |
| 16   | 80  | 0.12 | 0.4 | 1.462           | 3645.98 | 88.57  | 0.077 | 265.29 | 1.189               | 2700.73 | 75.06 | 0.090 | 187.70 |
| 17   | 80  | 0.12 | 0.6 | 0.399           | 4269.32 | 100.42 | 0.103 | 274.28 | 0.336               | 3162.45 | 85.10 | 0.120 | 194.07 |
| 18   | 80  | 0.12 | 0.8 | 1.732           | 5198.44 | 92.33  | 0.081 | 299.94 | 1.408               | 3850.70 | 78.25 | 0.095 | 212.22 |
| 19   | 110 | 0.08 | 0.4 | 1.562           | 5382.65 | 98.77  | 0.124 | 321.31 | 1.270               | 3987.14 | 83.70 | 0.145 | 227.34 |
| 20   | 110 | 0.08 | 0.6 | 0.637           | 4590.13 | 90.49  | 0.077 | 342.53 | 0.519               | 3400.10 | 76.69 | 0.090 | 242.35 |
| 21   | 110 | 0.08 | 0.8 | 1.387           | 5022.02 | 97.49  | 0.096 | 351.84 | 1.128               | 3720.02 | 82.62 | 0.113 | 248.94 |
| 22   | 110 | 0.1  | 0.4 | 0.420           | 4775.76 | 94.50  | 0.069 | 272.46 | 0.341               | 3537.60 | 80.08 | 0.081 | 192.78 |
| 23   | 110 | 0.1  | 0.6 | 1.238           | 5913.78 | 99.78  | 0.103 | 272.16 | 1.007               | 4380.58 | 84.56 | 0.120 | 192.56 |
| 24   | 110 | 0.1  | 0.8 | 2.588           | 3787.93 | 93.54  | 0.100 | 298.10 | 2.104               | 2805.88 | 79.27 | 0.117 | 210.92 |
| 25   | 110 | 0.12 | 0.4 | 1.139           | 3134.09 | 88.26  | 0.067 | 267.30 | 0.927               | 2321.55 | 74.79 | 0.079 | 189.13 |
| 26   | 110 | 0.12 | 0.6 | 0.551           | 4084.34 | 98.77  | 0.084 | 292.31 | 0.448               | 3025.44 | 83.70 | 0.099 | 206.82 |
| 27   | 110 | 0.12 | 0.8 | 0.584           | 5469.00 | 101.06 | 0.110 | 324.05 | 0.475               | 4051.11 | 85.64 | 0.128 | 229.28 |

A parametric analysis was conducted to compare the effects of cryogenic machining and flood machining on the machinability of Inconel 718. The key process parameters were varied to observe their impact on all selected machining responses. Figures 5 presents the results for the effect of cutting speed and feed rate on all these attributes, respectively.

From Figure 5, it is evident that cryogenic machining yields a smoother surface compared to flood machining. The reduction in surface roughness for cryogenic machining is attributed to better lubrication, which minimizes friction during the cutting process. At lower cutting speeds, surface roughness increases. However, beyond a speed of 50 m/min, the surface finish improves. This improvement is attributed to thermal softening of the material at higher speeds, which allows for a more effective removal of material flaws. Figure 5 also shows that cryogenic machining consumes less

power than flood machining. This difference arises because flood machining requires an additional pump to deliver a coolant and higher cutting forces are generated due to the excess friction in the machining zone. The power consumption increases with cutting speed and feed rate due to the higher energy demands required to maintain spindle rotation at increased cutting conditions. Previous study also supports this claim [44].

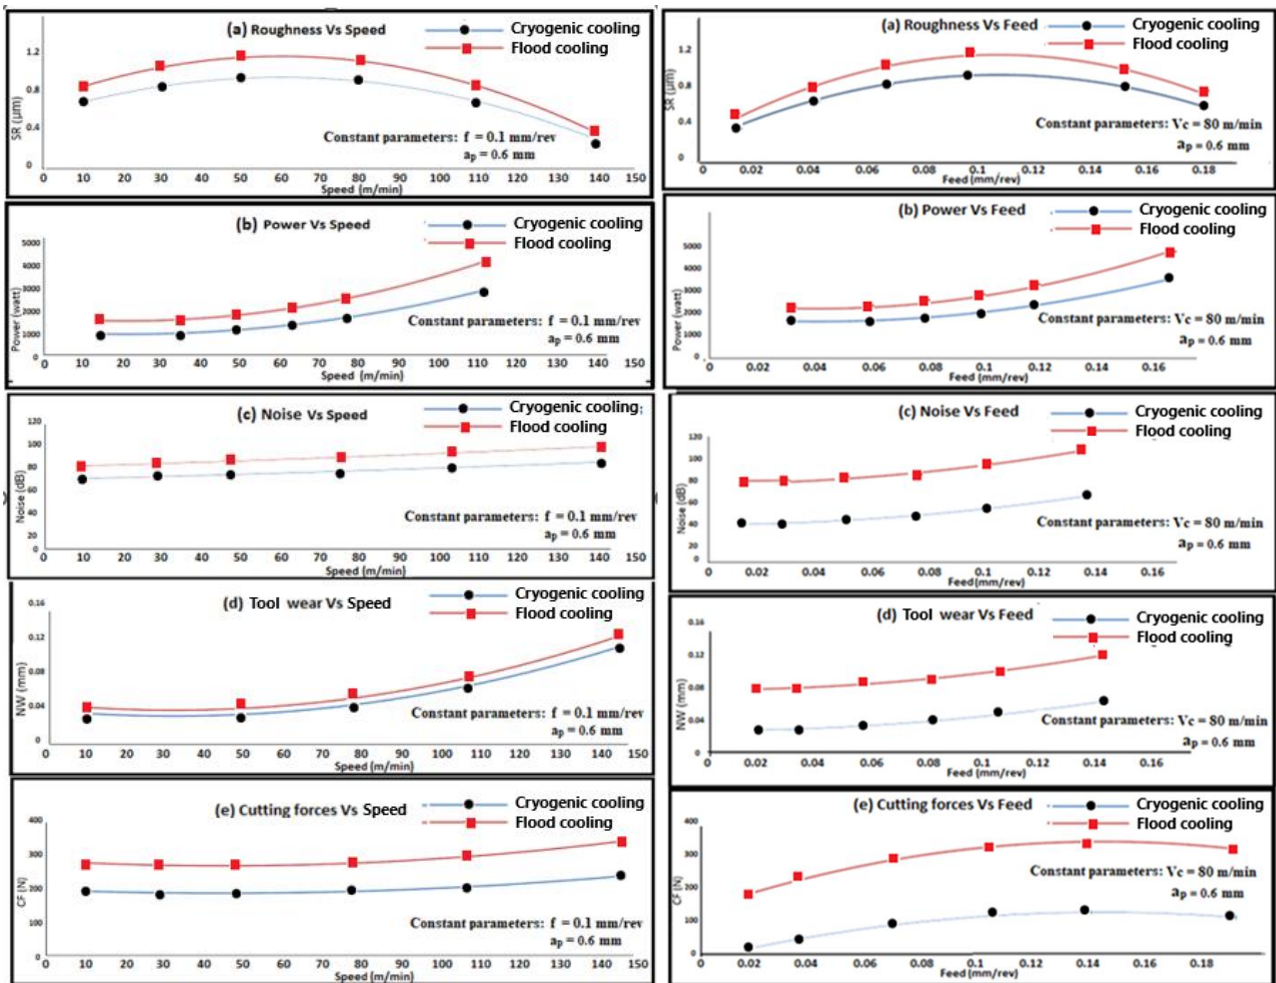

**Figure 5.** Effect of speed and feed on machining attributes.

Figure 5 also indicates that cryogenic machining results in lower machining noise compared to flood machining. This is because machining noise increases as cutting speed and feed rate are increased, due to higher levels of vibration and tool chatter. Figure 5 also demonstrates that tool wear is lower in cryogenic machining, as the reduced heat generation during machining results in less tool degradation. With increasing speed and feed rate, tool wear increases for both machining strategies, but cryogenic machining maintains wear levels within acceptable limits as defined by ISO standards [45]. Additionally, the cutting forces are lower for cryogenic machining due to less tool wear, maintaining sharp tool edges. Higher cutting speeds and feeds lead to an increase in cutting force due to the generation of tensile residual stresses in the workpiece. This is also supported by previous studies [46,47].

Similarly, the effect of depth of cut on the machining responses can be analysed in a similar manner, with expected trends aligning with the observed trends of cutting speed and feed. Based on the findings, cryogenic machining is shown to outperform flood machining in all key machinability characteristics when applied to Inconel 718, making it a superior choice.

#### 4.1 Main effect Plot for responses

To understand the influence of individual machining parameters on the measured responses, main effect plots were generated from the Taguchi  $L_{27}$  design data. These plots illustrate the average response values at each level of spindle speed, feed rate, and depth of cut, thereby revealing the general trend of how each factor affects surface roughness, tool wear, cutting forces, power consumption, and machining noise. Unlike interaction plots, main effect plots focus on the independent effect of each parameter, making them a useful tool for visualizing sensitivity and identifying optimal ranges of operation. The following subsections discuss the observed trends in detail for each response parameter.

The Figure 6 shows main effect plots reveal that surface roughness decreases with increasing cutting speed. This improvement is attributed to the thermal softening of the workpiece material at higher speeds, which facilitates smoother cutting and reduces adhesion at the tool-workpiece interface. Conversely, surface roughness shows a clear


increasing trend with higher feed rates. This can be explained by the fact that an increased feed imposes greater cutting loads on the tool, which in turn induces higher vibration and dynamic instability, thereby deteriorating surface finish.



**Figure 6.** Main effect plot for surface roughness.

The best surface finish is obtained at the combination of lowest feed rate and highest spindle speed. However, increasing the depth of cut results in a significant deterioration of surface finish. This behaviour arises from the excessive rubbing action between the tool and the workpiece, coupled with increased heat generation at higher depths of cut, which leads to a rise in surface roughness values.


Tool wear is another crucial response, as it directly influences the dimensional accuracy, surface integrity, and overall tool life, which in turn impacts the cost-effectiveness of machining. Among the various wear modes, nose wear plays a significant role as it leads to the retreat of the cutting edge and strongly affects the dimensional precision of the workpiece. Figure 7 illustrates the main effect plots for tool wear obtained under the present study, all of which remained within the acceptable limits defined by ISO 3658-1993 standards.

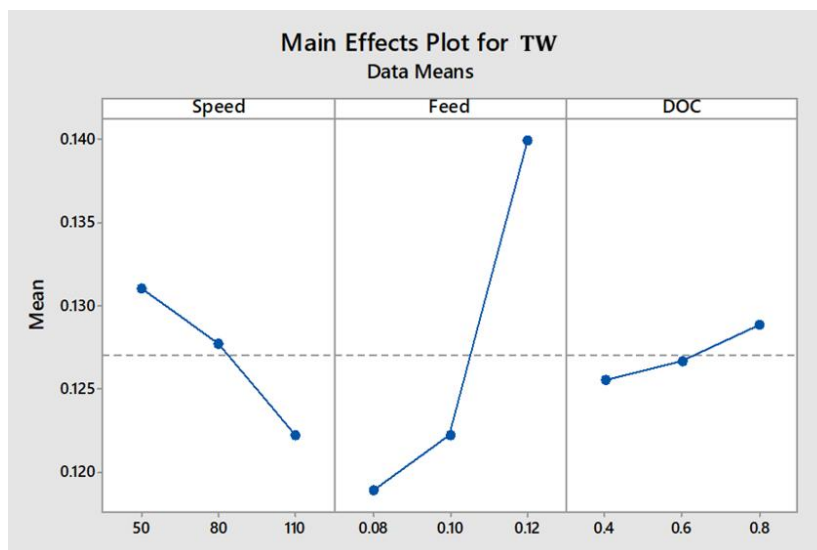

**Figure 7.** Main effect plot of Tool wear.

The plots indicate that tool wear decreases with increasing spindle speed. At a cutting speed of 110 m/min, the nose wear is reduced to as low as 0.122  $\mu\text{m}$ . Notably, tool wear at 110 m/min shows an approximate 25% reduction compared to the lower spindle speed of 50 m/min. This behavior can be attributed to improved chip removal and reduced cutting zone temperature under higher cutting speeds, which minimizes abrasive interaction at the tool-workpiece interface.

Cutting forces play a critical role in determining the stability of the machining system. Excessive forces can deform the workpiece, promote non-uniform chip formation, and compromise dimensional accuracy. Figure 8 presents the main effect plots for cutting forces, which clearly show that higher feed rates combined with lower spindle speeds lead to peak cutting force generation.

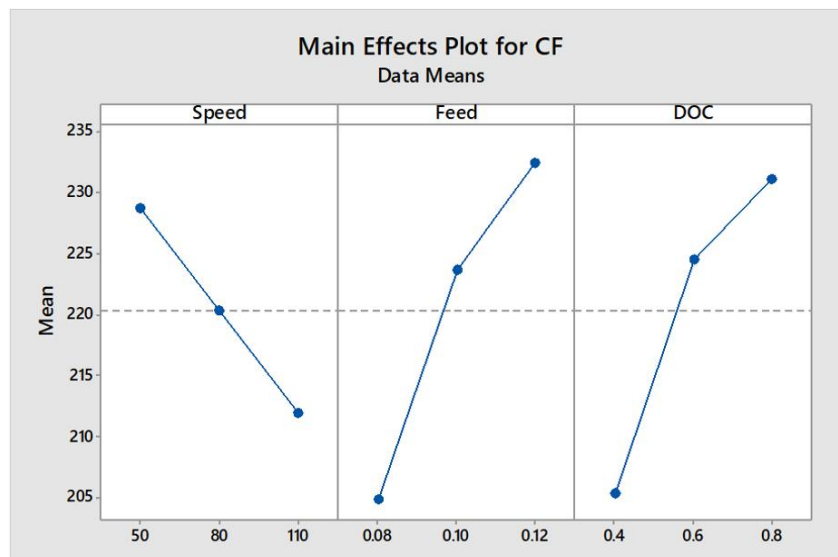

**Figure 8.** Main effect plot for cutting forces.

The maximum cutting force recorded was approximately 223 N at a spindle speed of 50 m/min, feed rate of 0.12 mm/rev, and depth of cut of 0.8 mm. In contrast, the lowest cutting force was observed under the cutting conditions of 110 m/min spindle speed, 0.08 mm/rev feed rate, and 0.4 mm depth of cut. This reduction at higher speeds and lower feeds can be attributed to reduced tool–workpiece contact stresses and improved chip evacuation. At lower cutting speeds, however, residual stresses induced in the workpiece tend to be tensile in nature, and with increased depth, these stresses elevate the cutting force requirements in the machining zone.

#### 4.2 Analysis of Variance for responses

The ANOVA results for surface roughness (SR), tool wear (TW), and cutting force (CF) are presented in Table 4. The analysis indicates that feed rate ( $f$ ) and depth of cut ( $ap$ ) are statistically significant ( $p < 0.05$ ) for all responses, whereas spindle speed ( $V_c$ ) has no significant effect ( $p > 0.05$ ).

This outcome is consistent with physical expectations: feed rate and depth of cut directly influence the chip load, tool–workpiece contact area, and cutting stresses, which in turn affect material removal mechanics, surface integrity, and tool wear under cryogenic machining conditions. The lack of statistical significance for spindle speed suggests that, within the tested range, it has a minor influence on heat generation and cutting dynamics compared to the dominant parameters, feed and depth of cut.

**Table 4.** ANOVA of machining parameters for SR, TW, and CF during cryogenic machining.


| Factor                  | SR      | SR      | TW      | TW      | CF      | CF      |
|-------------------------|---------|---------|---------|---------|---------|---------|
|                         | F-value | P-value | F-value | P-value | F-value | P-value |
| Cutting Speed ( $V_c$ ) | 0.22    | 0.802   | 0.75    | 0.483   | 0.84    | 0.448   |
| Feed( $f$ )             | 5.21    | 0.012   | 3.85    | 0.041   | 4.12    | 0.036   |
| Depth of Cut ( $ap$ )   | 6.47    | 0.006   | 4.92    | 0.019   | 7.35    | 0.004   |
| Error                   | –       | –       | –       | –       | –       | –       |

The F-values indicate the relative influence of each factor on the responses. For example, depth of cut exhibits the highest F-value for cutting force (7.35,  $p = 0.004$ ), confirming its strong impact on material removal forces. Feed rate also significantly affects SR, TW, and CF, highlighting its role in controlling tool engagement and surface finish quality. These results corroborate the observed experimental trends, where variations in feed and depth of cut caused notable changes in tool wear, cutting forces, and surface roughness, while changes in spindle speed produced comparatively minor effects.

In summary, the ANOVA analysis quantitatively validates the experimental observations, emphasizing that careful selection of feed rate and depth of cut is crucial for optimizing machining performance, precision, and sustainability in cryogenic turning of Inconel 718.

### 4.3 Scanning electron microscope (SEM) investigation


The post-machining modifications on the workpiece, worn-out inserts, and machined chips are examined using a scanning electron microscope (SEM) (Leica, S-430). The topography of the workpiece after machining following flood cooling and cryogenic machining is shown in Figures 9 (a) and (b), respectively. Compared to cryogenic approach, the SEM topography clearly demonstrates considerable damage to the machined surface during flood machining.

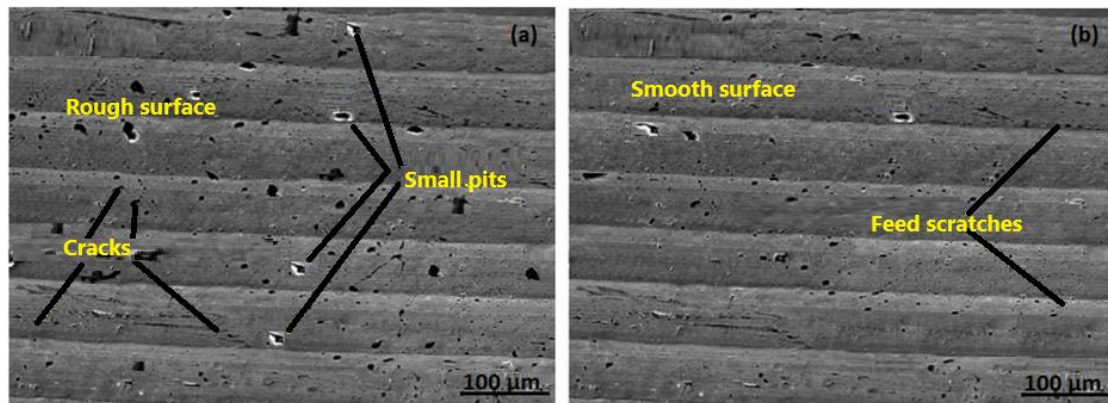

**Figure 9.** Surface features of Inconel 718 after: (a) flood machining, (b) cryogenic machining.

Additionally, it shows that the surface achieved by flood cooling has smaller pits and thin cracks that are far more intense than those seen on the cryogenic machined surface. Due to the higher friction at the cutting zone and inadequate lubrication, the flood cooled surface appears rough. However, surfaces that have undergone cryogenic machining have better surface quality, fewer thin cracks and pits. Previous investigations also support this claim [48].


SEM images of the worn-out tools during machining under flood cooling and cryogenic conditions are presented in Figure 10 (a) and (b), respectively. It is evident from these images that flood cooling results in more tool wear than cryogenic machining. This is because abrasion is the main cause of tool wear, which results in segment erosion as there is less lubrication during flood cooling. On the other hand, the cutting tool portion exhibits reduced erosion and abrasion in cryogenic machining. It also shows the erosion after a single trial i.e. 0.18 mm with high frittering tendency during flood cooling compared to the 0.11 mm with cryogenic cooling with no apparent wear on a cutting edge.

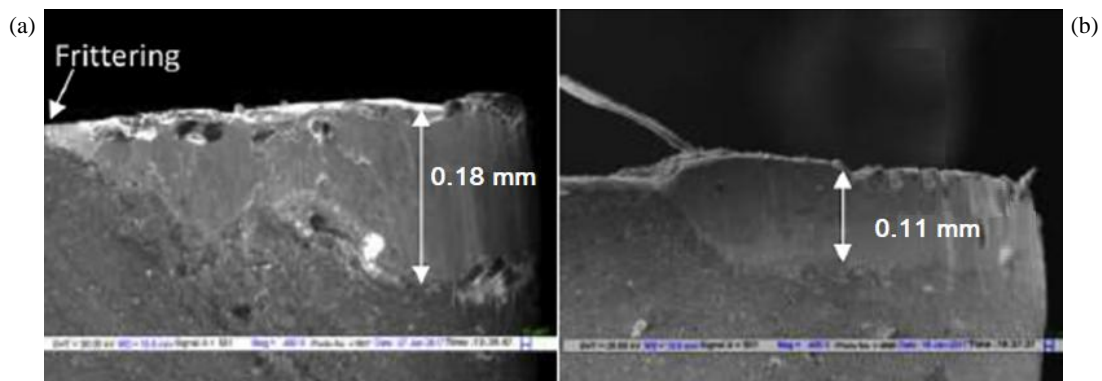


**Figure 10.** SEM micrographs of worn-out tools (a) flood cooled (b) cryogenic cooled.

### 4.4 Chip Morphology investigation

Chip morphology directly affects the surface integrity of machined part and clarifies important aspects of cutting mechanics. While maintaining constant input parameters, impacts of both machining processes on the morphologies of the chip of creation are also investigated in this work. Chips made for this purpose are examined using optical and SEM micrographs for both methods. The optical pictures of chips extracted using flood cooling and cryogenic cooling are depicted in Figure 11 (a) and (b) respectively. While the chip created during cryogenic machining is short and uniform, the chip created during flood cooling machining is shown to be twisted and wrenched. Furthermore, flood cooled chip had an uneven curvature and a rough back face due to built-up edges over the cutting plane. This clearly shows that cryogenic machining can minimize the wear of the cutting tools. Figure 12 (a) and (b) shows the micrographs of chips extracted using flood cooling and cryogenic cooling. It shows that chips generated with flood machined are distorted and non-uniformly segmented while cryogenic cooled chips are uniformly segmented. Previous studies also provided support for this claim [49,50].

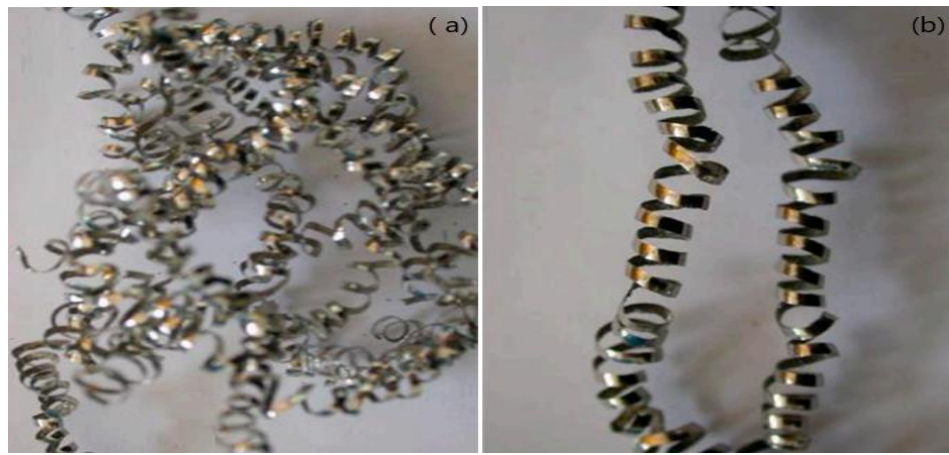

**Figure 11.** Optical images of chip formation. (a) MQL setup (b) cryogenic setup.

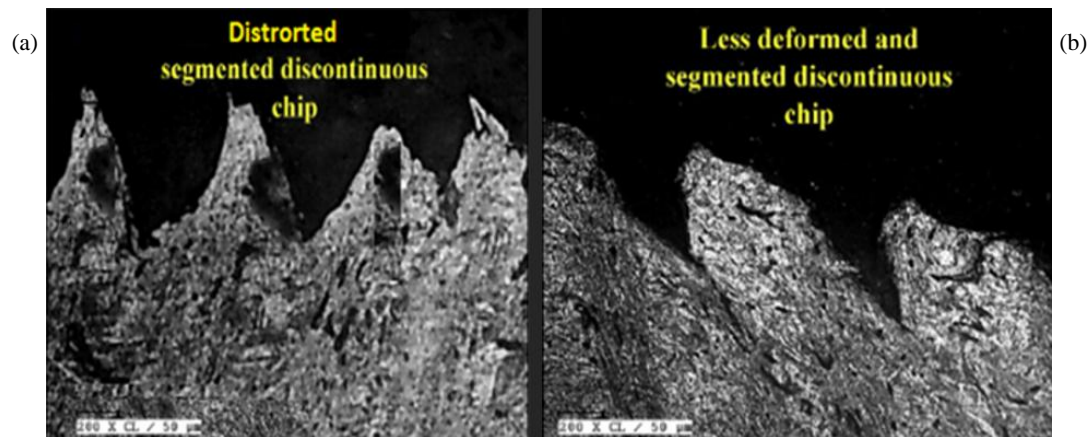

**Figure 12.** SEM images of chip. (a) flood machined, (b) cryogenic machined.

#### 4.5 Cost Assessment

**Table 5.** Cost comparison for flood machining and cryogenic machining.

| Sr. No. | Particular | Sub-category        | Flood machining cost (Rs)                                   | Cryogenic Machining cost (Rs)                               |
|---------|------------|---------------------|---|---|
| 1.      | Materials  | Cutting tool        | 4500<br>(Approx. 9 inserts; 500 Rs/ each)                   | 2000<br>(Approx. 4 inserts; 500 Rs/ each)                   |
|         |            | Coolant             | 3000<br>(Approx. 15 litres; 200 Rs/ Litre)                  | 800<br>(Approx 20 litres; 40 Rs/ Litre)                     |
| 2.      | Energy     | Machining Process   | 324<br>(27 units consumed)                                  | 252<br>(21 units consumed)                                  |
|         |            | Coolant circulation | Same  | Same  |
| 3.      | Waste      | Used inserts        | 450<br>(9 inserts; Approx 50Rs/ insert or<br>(1 Rs/gm rate) | 200<br>(4 inserts; Approx 50Rs/ insert or<br>(1 Rs/gm rate) |
|         |            | Used coolant        | 1500<br>(Rs. 100/litre)                                     | 0   |
| Total   |            |                     | 5274  | 3252  |

One of the important qualitative factors in determining how sustainable the turning process [51]. This study compares the overall cost of machining for flood cooling with cryogenic turning. Some of the crucial factors considered for the cost assessment analysis are the consumption of resources and energy, creation of waste and its disposal. The

computations from this section are predicated upon removal of 20 cm<sup>3</sup> of material using flood machining and cryogenic machining techniques after 27 trials. The comparative cost study between flood cooling and cryogenic machining is displayed in Table 5. The cost analysis for 27 trials conducted in accordance with the design of experiments highlights the primary cost components associated with flood and cryogenic machining strategies, namely materials, energy, and waste disposal. In the materials category, the cost of cutting tools for flood machining amounts to Rs. 4500, requiring approximately 9 inserts, compared to Rs. 2000 for cryogenic machining with 4 inserts. The coolant usage also shows a significant difference as flood machining consumes approximately 15 liters, costing around Rs. 3000, whereas cryogenic machining requires 20 liters of liquid nitrogen costing around Rs. 800.

The cost assumptions used in this analysis were based on a market survey and supplier quotations collected during July–August 2023 in Maharashtra, India. Cutting insert prices (Kennametal CNMG 120408-KC5010, ~Rs. 500 per insert) were obtained from a local distributor (Pune, Maharashtra). Coolant prices were sourced from certified suppliers, with neat cutting oil priced at ~Rs. 200 per litre (Kolhapur market, 2023) and liquid nitrogen at ~Rs. 40 per litre (supplier quotation, Sangli, 2023). Electricity tariffs were taken from the Maharashtra State Electricity Distribution Company Limited (MSEDCL) industrial slab rates valid during 2023. Waste disposal charges (Rs. 50 per insert or Rs. 1/gm, Rs. 100 per litre of used oil) were estimated from standard local industrial practices. These references provide transparency and industrial relevance to the cost comparison.

The energy consumption was evaluated for both machining operations and coolant circulation. The energy cost for machining with flood cooling was Rs. 324, with 27 units consumed, while cryogenic machining was more efficient, costing Rs. 252 for 21 units consumed. Coolant circulation costs remained consistent across both strategies. The waste disposal costs comprise the disposal of used cutting tools and coolant. For flood machining, 9 inserts were required, incurring a disposal cost of Rs. 450, reflecting the higher temperatures and inadequate lubrication in flood cooling (at an estimated Rs. 50 per insert or Rs. 1/gm rate, with each insert weighing approximately 50 gm as per standard disposal rates in India). In contrast, only 4 inserts were used in cryogenic machining, resulting in a lower disposal cost of Rs. 200. In terms of coolant disposal, flood machining incurs an additional cost of Rs.1500 for the disposal of 15 liters of used coolant at a rate of Rs. 100 per liter. This cost reflects the need for proper treatment and disposal due to the environmental and safety requirements associated with conventional coolants. Conversely, cryogenic machining eliminates this expense entirely, as liquid nitrogen disperses harmlessly into the atmosphere after contacting the machining zone, requiring no post-treatment or disposal. This advantage not only reduces costs but also highlights cryogenic machining as a more environmentally friendly approach, aligning with sustainable practices by avoiding hazardous waste generation and disposal. The cryogenic machining demonstrated cost efficiency, with a total expenditure of Rs. 3252 compared to Rs. 5274 for flood machining. This comparison provides valuable insights for industrial applications, supporting the shift towards advanced machining techniques that balance productivity with sustainability. This is also supported by previous research [52].

## 5. Conclusion

This study demonstrates that cryogenic machining offers substantial advantages over conventional flood cooling for the precision machining of Inconel 718. The approach improved tool life, reduced energy consumption, and eliminated the need for coolant disposal, thereby enhancing both machining efficiency and environmental performance.

Key outcomes include:

Up to 30% reduction in surface roughness, particularly at higher cutting speeds due to thermal softening effects.

About 10% lower machining noise, linked to reduced vibration and cutting forces.

30% decrease in tool nose wear across all parameter levels, maintaining values within ISO standards.

On average, 15% lower cutting forces, as sharper tool edges were retained under cryogenic conditions.

A 38% reduction in total machining cost, largely due to lower tool consumption and absence of coolant disposal expenses.

Beyond the immediate industrial applications, these findings also contribute to advancing research in sustainable machining practices, providing a framework for integrating precision performance with environmental responsibility in next-generation manufacturing systems. These findings also highlight cryogenic machining as a viable and sustainable strategy for high-precision, high-value industries such as aerospace, defence, and energy, where dimensional accuracy and surface integrity are critical. Future work may focus on hybrid cooling strategies (e.g., LN<sub>2</sub>-assisted MQL) and life cycle assessment (LCA) studies to comprehensively evaluate the long-term industrial and environmental benefits of cryogenic cooling.

## Conflicts of Interest

The authors declare no conflicts of interest.

## Generative AI Statement

The authors declare that no generative artificial intelligence (Gen AI) was used in the creation of this manuscript.

## Reference

- [1] Chetan, Ghosh S, Rao PV. Environment friendly machining of Ni–Cr–Co based superalloy using different sustainable techniques. *Materials and Manufacturing Processes*, 2015, 31(7), 852-859. DOI: 10.1080/10426914.2015.1037913
- [2] Kalin M, Polajnar M, Kus M, Majdič F. Green Tribology for the Sustainable Engineering of the Future. *Journal of Mechanical Engineering/Strojniški Vestnik*, 2019, 65(11-12), 709-727. DOI: 10.5545/sv-jme.2019.6406
- [3] De Bartolomeis A, Newman S, Shokrani A. State-of-the-art cooling and lubrication for machining Inconel 718. *Journal of Manufacturing Science and Engineering*, 2021, 143(5), 050801. DOI: 10.1115/1.4047842
- [4] Dhar NR, Paul S, Chattopadhyay AB. Role of cryogenic cooling on cutting temperature in turning steel. *Journal of Manufacturing Science and Engineering*, 2002, 124(1), 146-154. DOI: 10.1115/1.1413774
- [5] Jadhav PS, Mohanty CP. Comparative analysis of indirect, direct and hybrid cryogenic machining of Nimonic C-263 superalloy. *Journal of Engineering Research*, 2022, 10(4B). DOI: 10.36909/jer.11687
- [6] Jadhav PS, Mohanty CP. Performance assessment of energy efficient and eco-friendly turning of Nimonic C-263: A comparative study on MQL and cryogenic machining. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, 2022, 236(8), 1125-1140. DOI: 10.1177/09544054211061961
- [7] Jadhav PS, Mohanty CP, Hotta TK, Gupta M. An optimal approach for improving the machinability of Nimonic C-263 superalloy during cryogenic assisted turning. *Journal of Manufacturing Processes*, 2020, 58, 693-705. DOI: 10.1016/j.jmapro.2020.08.017
- [8] Jadhav PS, Mohanty CP, Shirguppikar SS. Cryogenic treatment of Nimonic alloy-hard turning: state-of-the-art, challenges and future directions. *Materials Today: Proceedings*, 2019, 18, 4120-4132. DOI: 10.1016/j.matpr.2019.07.356
- [9] Jamil MF, Sahto MP, Mehmood A. Comprehensive study on high-performance machining (HPM) of Inconel-718: a review. *The International Journal of Advanced Manufacturing Technology*, 2025, 139, 5305-5337. DOI: 10.1007/s00170-025-16225-z
- [10] Kaynak Y. Evaluation of machining performance in cryogenic machining of Inconel 718 and comparison with dry and MQL machining. *International Journal of Advanced Manufacturing Technology*, 2014, 72, 919-933. DOI: 10.1007/s00170-014-5683-0
- [11] Sinha MK, Pal A, Kishore K, Singh A, Archana, et al. Applications of sustainable techniques in machinability improvement of superalloys: a comprehensive review. *International Journal on Interactive Design and Manufacturing*, 2023, 17, 473-498. DOI: 10.1007/s12008-022-01053-2
- [12] Korkmaz ME, Gupta MK. A State of the Art on Cryogenic Cooling and Its Applications in the Machining of Difficult-to-Machine Alloys. *Materials*, 2024, 17(9), 2057. DOI: 10.3390/ma17092057
- [13] Soori M, Arezoo B. The effects of coolant on the cutting temperature, surface roughness and tool wear in turning operations of Ti6Al4V alloy. *Mechanics Based Design of Structures and Machines*, 2023, 52(6), 3277–3299. DOI: 10.1080/15397734.2023.2200832
- [14] Khan MA, Jaffery SHI. Specific cutting energy and surface roughness analysis of dry, wet and cryogenic turning of Ti-6Al-4V. *Procedia CIRP*, 2025, 135, 538-542. DOI: 10.1016/j.procir.2024.12.050
- [15] Mia M, Dey PR, Zobaer ST, Taguchi S/N based optimization of machining parameters in hard turning under MQL cutting condition. *Measurement*, 2018, 122, 380-391. DOI: 10.1016/j.measurement.2018.02.016
- [16] Gao Z, Zhang H, Ji M, Zuo C, Zhang J. Influence of various cooling and lubrication conditions on tool wear and machining quality in milling Inconel 718. *International Journal of Precision Engineering and Manufacturing-Green Technology*, 2024, 11(2), 391–406. DOI: 10.1007/s40684-023-00558-9
- [17] Musavi SH, Davoodi B, Niknam SA. Effects of reinforced nanoparticles with surfactant on surface quality and chip formation morphology in MQL-turning of superalloys. *Journal of Manufacturing Processes*, 2019, 40, 128-139. DOI: 10.1016/j.jmapro.2019.03.014
- [18] Nguyen TT, Le CH. Optimization of compressed air assisted-turning-burnishing process for improving machining quality, energy reduction and cost-effectiveness. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, 2020, 235(6-7), 1179-1196. DOI: 10.1177/0954405420976661
- [19] Ali S, Abdallah S, Pervaiz S, Deiab I. Progress on sustainable cryogenic machining of hard-to-cut material and greener processing techniques: A combined machinability and sustainability perspective. *Lubricants*, 2025, 13(8), 322. DOI: 10.3390/lubricants13080322
- [20] Pušavec F, Deshpande A, Yang S, M'Saoubi R, Kopač J, et al. Sustainable machining of high temperature Nickel alloy-Inconel 718: part 1-predictive performance models. *Journal of Cleaner Production*, 2014, 81, 255-269. DOI: 10.1016/j.jclepro.2014.06.040
- [21] Seid Ahmed Y, Amorim FL. Advances in computer numerical control geometric error compensation: integrating AI and on-machine technologies for ultra-precision manufacturing. *Machines*, 2025, 13(2), 140. DOI: 10.3390/machines13020140
- [22] Pušavec F, Hamdi H, Kopač J, Jawahir IS. Surface integrity in cryogenic machining of nickel based alloy-Inconel 718. *Journal of Materials Processing Technology*, 2011, 211(4), 773-783. DOI: 10.1016/j.jmatprotec.2010.12.013
- [23] Virdi RL, Chatha SS, Singh H. Machining performance of Inconel-718 alloy under the influence of nanoparticles based minimum quantity lubrication grinding. *Journal of Manufacturing Processes*, 2020, 59, 355–365. DOI: 10.1016/j.jmapro.2020.09.056
- [24] Korkmaz ME, Gupta MK. A state of the art on cryogenic cooling and its applications in the machining of difficult-to-machine alloys. *Materials*, 2024, 17(9), 2057. DOI: 10.3390/ma17092057
- [25] Zhang Y, Li C. Machining performance of alloy difficult-to-cut materials. In: *Hybrid-Energy Sustainable Machining: Mechanism and Processability*. Springer, Singapore, 2025, pp. 553-592. DOI: 10.1007/978-981-96-7026-0\_12
- [26] Zhang L, Jiang Z, Zhu S, Yang Z, Zhang H, et al. An energy consumption field model considering motion position errors for energy efficient machining on CNC machines: CNC programming perspective. *Applied Energy*, 2024, 374, 124023. DOI: 10.1016/j.apenergy.2024.124023
- [27] Sharma VS, Dogra M, Suri NM. Cooling techniques for improved productivity in turning. *International Journal of Machine Tools and Manufacture*, 2017, 29, 201–211. DOI: 10.1016/j.ijmachtools.2008.12.010

- [28] Suarez MP, Marques A, Boing D, Amorim FL, Machado ÁR. MoS<sub>2</sub> solid lubricant application in turning of AISI D6 hardened steel with PCBN tools. *Journal of Manufacturing Processes*, 2019, 47, 337-346. DOI: 10.1016/j.jmapro.2019.10.001
- [29] Zhu L, Nie S, Huang H, Xia J, Liu Z. A hybrid modeling approach for Ti-6Al-4V turning under a high-pressure CO<sub>2</sub> cryogenic cooling jet. *The International Journal of Advanced Manufacturing Technology*, 2025, 139, 1203-1218. DOI: 10.1007/s00170-025-15959-0
- [30] Yıldırım ÇV, Kivak T, Erzincanlı F. Tool wear and surface roughness analysis in milling with ceramic tools of Waspaloy: a comparison of machining performance with different cooling methods. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 2019, 41, 83. DOI: 10.1007/s40430-019-1582-5
- [31] Hong SY. Economical and ecological cryogenic machining. *Journal of Manufacturing Science and Engineering*, 2001, 123(2), 331-338. DOI: 10.1115/1.1315297
- [32] Danish M, Gupta MK, Rubaiee S, Ahmed A, Korkmaz ME. Influence of hybrid Cryo-MQL lubri-cooling strategy on the machining and tribological characteristics of Inconel 718. *Tribology International*, 2021, 163, 107178. DOI: 10.1016/j.triboint.2021.107178
- [33] Zaman P, Sultana M, Dhar N. Quantifying the effects of cooling condition and cutting parameters in turning AISI 4140 steel. *Journal of Production Systems and Manufacturing Science*, 2020, 1(2), 9-18.
- [34] Korkmaz ME, Gupta MK, Çelik E, Ross NS, Günay M. A sustainable cooling/lubrication method focusing on energy consumption and other machining characteristics in high-speed turning of aluminum alloy. *Sustainable Materials and Technologies*, 2024, 40, e00919. DOI: 10.1016/j.susmat.2024.e00919
- [35] Wang ZY, Rajurkar KP, Fan J, Lei S, Shin YC, Petrescu G. Hybrid machining of Inconel 718. *International Journal of Machine Tools and Manufacture*, 2003, 43(13), 1391-1396. DOI: 10.1016/S0890-6955(03)00134-2
- [36] Tebaldo V, di Confienzo GG, Faga MG. Sustainability in machining: “Eco-friendly” turning of Inconel 718. *Surface characterisation and economic analysis*. *Journal of Cleaner Production*, 2017, 140, 1567-1577. DOI: 10.1016/j.jclepro.2016.09.216
- [37] Ramena DVP, Vikram KA, Chebolu R, Barmavatu P, Sikarwar VS, et al. Sustainable green cutting fluid for interpreting optimization of process variables while machining on various CNC manufacturing systems-an experimental approach for exploring. *International Journal of Advanced Manufacturing Technology*, 2025, 136, 329-342. DOI: 10.1007/s00170-024-14028-2
- [38] Suhaimi MA, Sarhan AAD. Sustainable machining of aerospace materials. *Journal of Cleaner Production*, 2015, 108, 245-255. DOI: 10.1016/j.jclepro.2015.06.049
- [39] Sivalingam V, Liu H, Selvam B, Kai G, Kumar PG, et al. Towards sustainability assessment, energy consumption, and carbon emissions in cryogenic drilling of Alloy 20: a new approach towards sustainable future and challenges. *International Journal of Advanced Manufacturing Technology*, 2024, 131, 1151-1165. DOI: 10.1007/s00170-024-13144-3
- [40] Kaynak Y. Evaluation of machining performance in cryogenic machining of Inconel 718 and comparison with dry and MQL machining. *International Journal of Advanced Manufacturing Technology*, 2014, 72, 919-933. DOI: 10.1007/s00170-014-5683-0
- [41] Chetan, Ghosh S, Rao PV. Environment Friendly Machining of Ni-Cr-Co Based Super Alloy using Different Sustainable Techniques. *Materials and Manufacturing Processes*, 2015, 31(7), 852-859. DOI: 10.1080/10426914.2015.1037913
- [42] Shokrani A, Dhokia V, Newman ST. Energy conscious cryogenic machining of Ti-6Al-4V titanium alloy. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, 2016, 232(10), 1690-1706. DOI: 10.1177/0954405416668923
- [43] Chaabani S, Arrazola PJ, Ayed Y, Madariaga A, Tidu A, Germain G. Comparison between cryogenic coolants effect on tool wear and surface integrity in finishing turning of Inconel 718. *Journal of Materials Processing Technology*, 2020, 285, 116780. DOI: 10.1016/j.jmatprotec.2020.116780
- [44] Ajay P, Dabhade VV. Heat treatments of Inconel 718 nickel-based superalloy: a review. *Metals and Materials International*, 2025, 31, 1204-1231. DOI: 10.1007/s12540-024-01812-8
- [45] Khanna N, Airao J, Kshitij G, Nirala CK, Hegab H. Sustainability analysis of new hybrid cooling/lubrication strategies during machining Ti6Al4V and Inconel 718 alloys. *Sustainable Materials and Technologies*, 2023, 36, e00606. DOI: 10.1016/j.susmat.2023.e00606
- [46] Yaqoob S, Ghani JA, Juri AZ, Muhamad SS, Haron CHC, et al. A review of sustainable hybrid lubrication (Cryo-MQL) techniques in machining processes. *International Journal of Advanced Manufacturing Technology*, 2024, 131(1), 151-169. DOI: 10.1007/s00170-024-13135-4
- [47] Damir A, Shi B, Elsayed A, Thelin J, M'Saoubi R, et al. On the tribological and thermal aspects of cryogenic machining of Inconel 718 and their effects on surface integrity. *Wear*, 2025, 571, 205855. DOI: 10.1016/j.wear.2025.205855
- [48] Younas M, Khan M, Jaffery SHI, Khan Z, Khan N. Investigation of tool wear and energy consumption in machining Ti6Al4V alloy with uncoated tools. *International Journal of Advanced Manufacturing Technology*, 2024, 132(7), 3785-3799. DOI: 10.1007/s00170-024-13548-1
- [49] De Bartolomeis A, Newman ST, Biermann D, Shokrani A. State-of-The-Art Cooling and Lubrication for Machining Inconel 718. *Journal of Manufacturing Science and Engineering*, 2021, 143(5), 050801. DOI: 10.1115/1.4047842
- [50] Makhesana MA, Patel KM, Bagga PJ. Evaluation of Surface Roughness, Tool Wear and Chip Morphology during Machining of Nickel-Based Alloy under Sustainable Hybrid Nanofluid-MQL Strategy. *Lubricants*, 2022, 10(11), 315. DOI: 10.3390/lubricants10110315
- [51] Pedroso AF, Sousa VF, Sebbe NP, Silva FJ, Campilho RD, et al. Cooling and lubricating strategies for INCONEL® alloys machining: a comprehensive review on recent advances. *Journal of Tribology*, 2025, 147(6), 060801. DOI: 10.1115/1.4066955
- [52] Meddour I, Yaltese MA, Khattabi R, Elbah M, Boulanour L. Investigation and modeling of cutting forces and surface roughness when hard turning of AISI 52100 steel with mixed ceramic tool: cutting conditions optimization. *International Journal of Advanced Manufacturing Technology*, 2015, 77 1387-1399. DOI: 10.1007/s00170-014-6559-z